



4700 Broadmoor SE, Suite 200  
Kentwood, MI 49512

Telephone: 616-656-7401  
Facsimile: 616-656-2022  
www.intertek-etlsemko.com

FUNDERMAX GMBH  
Date:  
P.O. No.: MP

**DRAFT**

Report No.: 101666076GRR-001B  
Reference No.: 14-500530170  
Page 1 of 7

**Test Report For:**

**FunderMax GmbH**

**Specimen ID: 0082 Tiefachwarz**

**Max Resistance Ansichtsmuster, Aberfl FM Starke 25  
mm**

**SEFA 3-2010, 2.1 Chemical/Stain Resistances**

---

**Gary Liu**  
**Project Manager**

---

**Tom Pearson**  
**Reviewer**

**DRAFT:**

*Intertek's responsibility and liability are limited to the terms and conditions of the agreement. Intertek assumes no liability to any party, other than to the Client in accordance with the agreement, for any loss, expense or damage occasioned by the use of this information. Any observations and results in this report are relevant only to the sample tested. Only the Client is authorized to copy and distribute this information and only then in its entirety and accompanied by the associated full report.*



Intertek



Intertek



Intertek



Intertek



Intertek



Intertek



Intertek



FUNDERMAX GMBH .  
Date:  
P.O. No.: EK

**DRAFT**

Report No.: 101666076GRR-001B  
Reference No.: 14-500530170  
Page 2 of 8

Attention: Arnulf Penker  
FUNDERMAX GMBH  
Klagenfurter Strasse 87-89  
A-9300 Klagenfurt  
Austria  
Phone: 43594944550  
E-Mail: armulf.penker@fundermax.biz

**DATE RECEIVED:** 05/20/14  
**DATES TESTED:** 06/11/14 - 06/12/14

**DESCRIPTION OF SAMPLES:**

Specimen ID: 0082 Tiefachwarz  
Part Description: Max Resistance Ansichtsmuster, Aberfl FM Starke 25 mm  
Material Submitted: Four (4) of ~ 4" x 12" Laminated Black Sections  
Material Specification: SEFA 3-2010  
Condition of Test Sample: Production

**WORK REQUESTED / APPLICABLE DOCUMENTS:**

2.1 Chemical/Stain Resistances: SEFA 3-2010, Section 2.1

**CONCLUSIONS:**

2.1 Chemical/Stain Resistances: Conforming\*

\* Suitability for a given application is dependent upon the chemicals used in a given laboratory.

**DISPOSITION OF TEST SPECIMENS/ SAMPLES:**

Test samples were properly disposed.

## **2.1 CHEMICAL/STAIN RESISTANCES:**

Date Received: 05/20/14  
Dates Tested: 06/11/14 - 06/12/14

### Description of Samples:

Specimen ID: 0082 Tiefachwarz  
Part Description: Max Resistance Ansichtsmuster, Aberfl FM Starke 25 mm  
Material Submitted: Four (4) of ~ 4" x 12" Laminated Black Sections  
Material Specification: SEFA 3-2010  
Condition of Test Sample: Production

### Test Procedure:

Test Method: SEFA 3-2010, Sec 2.1  
The received sample to be tested for chemical resistance as described herein: Place panel on flat surface, clean with soap (Liqui-Nox at 5% concentration) and water and blot dry. Condition the panel for 48-hours at 73±3°F (23±2°C) and 50 ± 5% relative humidity. Test the panel for chemical resistance using forty-nine (49) different chemical reagents by the following methods.

Method A: For volatile chemicals – A cotton ball, saturated with the test chemical, was placed in a one ounce bottle (10mm x 7mm test tube or similar container). The container was inverted on the test material surface for a period of 24 hours. Temperature of test: 23° +/- 2°C (73° +/- 4°F). This method was used for the organic solvents.

Method B: For non-volatile chemicals – Five drops (1/4cc) of the test chemical were placed on the test material surface. The chemical was covered with a watch glass (25mm), convex side down for a period of 24 hours. Temperature of test: 23° +/- 2°C (73° +/- 4°F). This method was used for all chemicals listed below other than solvents.

After 24-hours exposure, exposed areas were washed with water, then a detergent solution detergent (Liqui-Nox at 5% concentration) and finally with isopropyl alcohol. Materials were then rinsed with distilled water and dried with a cloth.  
Test Side: Both sides are able to be tested per client

Chemical/Stain Resistances Test Procedure:

Samples are numerically rated as follows:

**0 – No Effect** – No detectable change in the material surface.

**1 – Excellent** – Slight detectable change in color or gloss but no change in function or life of the surface.

**2 – Good** – A clearly discernible change in color or gloss but no significant impairment of surface life or function.

**3 – Fair** – Objectionable change in appearance due to discoloration or etch, possibly resulting in deterioration of function over an extended period of time.

Number of Samples Tested: Four (4) panels

Acceptance Criteria:

Results will vary from manufacturer to manufacturer due to differences in composition and finish formulations and applications processes. Laboratory Grade work surface finishes shall result in no more than 4 Level 3 conditions. Individual test results for the specified 49 reagents will be verified with an established third party independent SEFA 3 test submittal form. Suitability for a given application is dependent upon the chemicals used in a given laboratory.

Results:

2.1 CHEMICAL/STAIN RESISTANCES				
Volatile Chemicals				
Test No.	Chemical	Method	Rating	Comments
1	Acetate, Amyl	A	0	
2	Acetate, Ethyl	A	0	
4	Acetone	A	1	Slight Color Change
6	Alcohol, Butyl	A	0	
7	Alcohol, Ethyl	A	0	
8	Alcohol, Methyl	A	0	
10	Benzene	A	0	
11	Carbon Tetrachloride	A	0	
12	Chloroform	A	1	Slight color and gloss change
14	Cresol	A	1	Gloss decrease
15	Dichloroacetic Acid	A	2	Gloss decrease
16	Dimethylformamide	A	0	
17	Dioxane	A	0	
18	Ethyl Ether	A	0	
19	Formaldehyde, 37%	A	0	
21	Furfural	A	1	Color change

DRAFT

**2.1 CHEMICAL/STAIN RESISTANCES****Volatile Chemicals**

Test No.	Chemical	Method	Rating	Comments
22	Gasoline	A	0	
27	Methyl Ethyl Ketone	A	0	
28	Methylene Chloride	A	0	
29	Monochlorobenzene	A	0	
30	Naphthalene	A	0	
34	Phenol, 90%	A	1	Gloss decrease
46	Toluene	A	0	
47	Trichloroethylene	A	0	
48	Xylene	A	0	

**2.1 CHEMICAL/STAIN RESISTANCES****Non-volatile Chemicals**

Test No.	Chemical	Method	Rating	Comments
3	Acetic Acid, 98%	B	0	
5	Acid Dichromate, 5%	B	1	Slight color change
9	Ammonium Hydroxide, 28%	B	0	
13	Chromic Acid, 60%	B	0	
20	Formic Acid, 90%	B	1	Gloss decrease
23	Hydrochloric Acid, 37%	B	0	
24	Hydrofluoric Acid, 48%	B	1	Color change
25	Hydrogen Peroxide, 30%	B	2	Color Change
26	Iodine, Tincture of	B	1	Gloss Decrease
31	Nitric Acid, 20%	B	0	
32	Nitric Acid, 30%	B	0	
33	Nitric Acid, 70%	B	0	
35	Phosphoric Acid, 85%	B	0	
36	Silver Nitrate, Saturated	B	0	
37	Sodium Hydroxide, 10%	B	0	
38	Sodium Hydroxide, 20%	B	0	
39	Sodium Hydroxide, 40%	B	0	
40	Sodium Hydroxide, Flake	B	0	
41	Sodium Sulfide, Saturated	B	0	
42	Sulfuric Acid, 33%	B	0	

<b>2.1 CHEMICAL/STAIN RESISTANCES</b>				
<b>Non-volatile Chemicals</b>				
<b>Test No.</b>	<b>Chemical</b>	<b>Method</b>	<b>Rating</b>	<b>Comments</b>
43	Sulfuric Acid 77%	B	0	
44	Sulfuric Acid, 96%	B	1	Gloss decrease
45	Sulfuric Acid, (77%) and Nitric Acid (70%), equal parts	B	2	Color and gloss change
49	Zinc Chloride, Saturated	B	0	

<b>2.1 CHEMICAL/STAIN RESISTANCES</b>			
<b>Totals</b>			
<b>Items</b>	<b>Requirement</b>	<b>No. Reagent with 3 Ratings</b>	<b>Disposition</b>
Volatile Subtotal:	-	0	
Non-volatile Subtotal:	-	0	
Grand Totals:	No More than Four Level 3 Conditions	0	Conforming*

\* Suitability for a given application is dependent upon the chemicals used in a given laboratory.

## 2.1 Chemical/Stain Resistances Photographs



Setup non-volatile chemicals




Setup volatile chemicals

## 2.1 Chemical/Stain Resistances Photographs



Post-exposure non-volatile chemicals

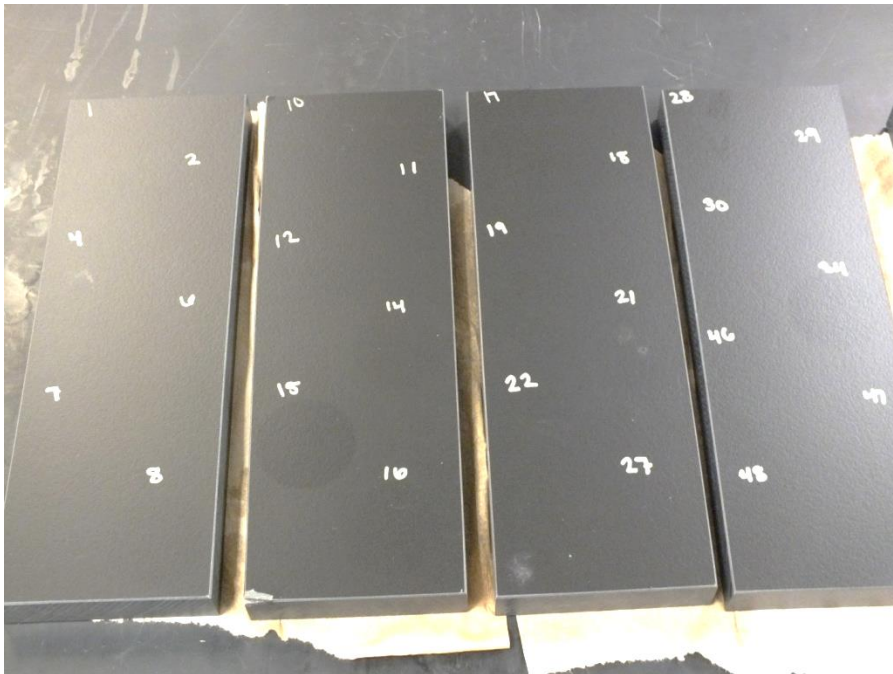

Post-exposure volatile chemicals